

Technical Data Sheet: TLH-0

TDS-TLH-0-v1.2

1. Overview:

- ❖ **Type:** Highlands
- ❖ **Series:** TerraLun™- Core
- ❖ **Composition:**
 - Anorthosite
 - Basalt
 - Altered Peridotite
- ❖ **Mean NASA FoM Score:** 91.7%
- ❖ **100 % European** Sourced & Manufactured.
- ❖ **Uses:** High-fidelity general simulant suitable for geotechnical and mobility testing, excavation and construction trials, large-scale testbeds, ISRU process development, dust and environmental studies, filtration and sealing validation, scientific research, and technology demonstration.

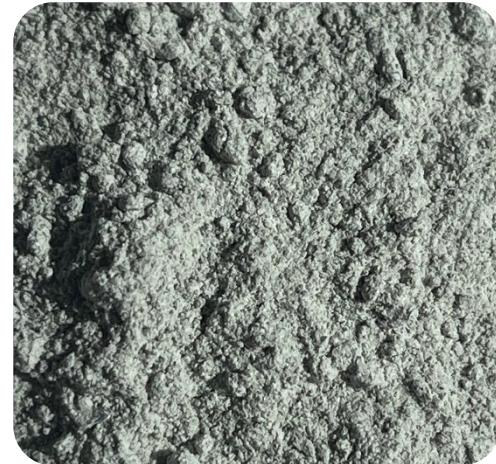


Figure 1: TLH-0 Close-up View

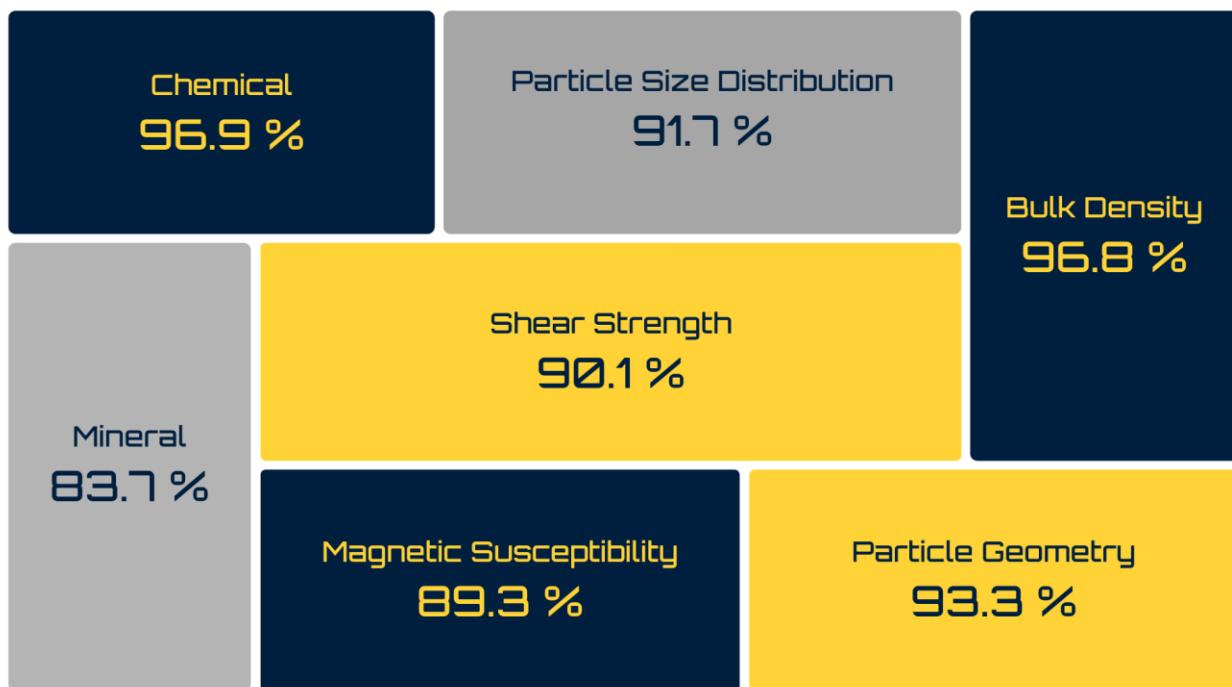


Figure 2: NASA Figures of Merit Results for TLH-0

2. Product Characterization

2.1 Chemical Composition

Chemical composition obtained through X-ray fluorescence analysis (XRF) performed by UPV/EHU with a Bruker M4 TORNADO.

SiO ₂	TiO ₂	Al ₂ O ₃	FeO	MgO	CaO	Na ₂ O	K ₂ O	SrO	MnO	Cr ₂ O ₃	NiO	ZnO
46.43	0.82	25.06	6.78	5.09	14.13	0.00*	0.67	0.25	0.14	0.11	0.01	0.19

Table 1: Chemical Composition of TLH-0

*Na₂O is expected to be present according to the mineral composition, but it might be below the identification and quantification limit of this machine.

2.2 Mineral Composition

Mineral composition and quantification of glass/amorphous fraction through X-Ray Diffraction analysis (XRD) performed at UCLM by Jacinto Alonso-Azcarate with a PANalytical Xpert PRO machine. Supplemented by a Raman Spectroscopy performed at UPV/EHU with a Raman Renishaw InVia micro spectrometer.

Anorthite	Augite	Fosterite	Lizardite	Analcime	Smectite	Illite	Quartz	Hornblende	Amorphous/ Glass
57	5.7	1.8	6.5	2.6	0.5	1	1.2	2.1	19.2

Table 2: Mineral Composition of TLH-0

Pyroxene	Plagioclase Feldspar	Olivine	Ilmenite	Glass
5.7	57	1.8	0	19.2

Table 3: Mineral Group Classification of TLH-0

2.3 Bulk Density

Minimum, maximum and mean density measured in-house.

Minimum Density : 1.40 g/cm³

Maximum Density: 1.94g/cm³

Mean Density: 1.67 g/cm³


2.4 Particle Size Distribution

Particle size distribution (PSD) measured through Dynamic Image Analysis performed by a third-party entity with a CAMSIZER X2.

Range: 0.03-3000 µm

Median: 137.60 µm

Mean: 390.50 µm

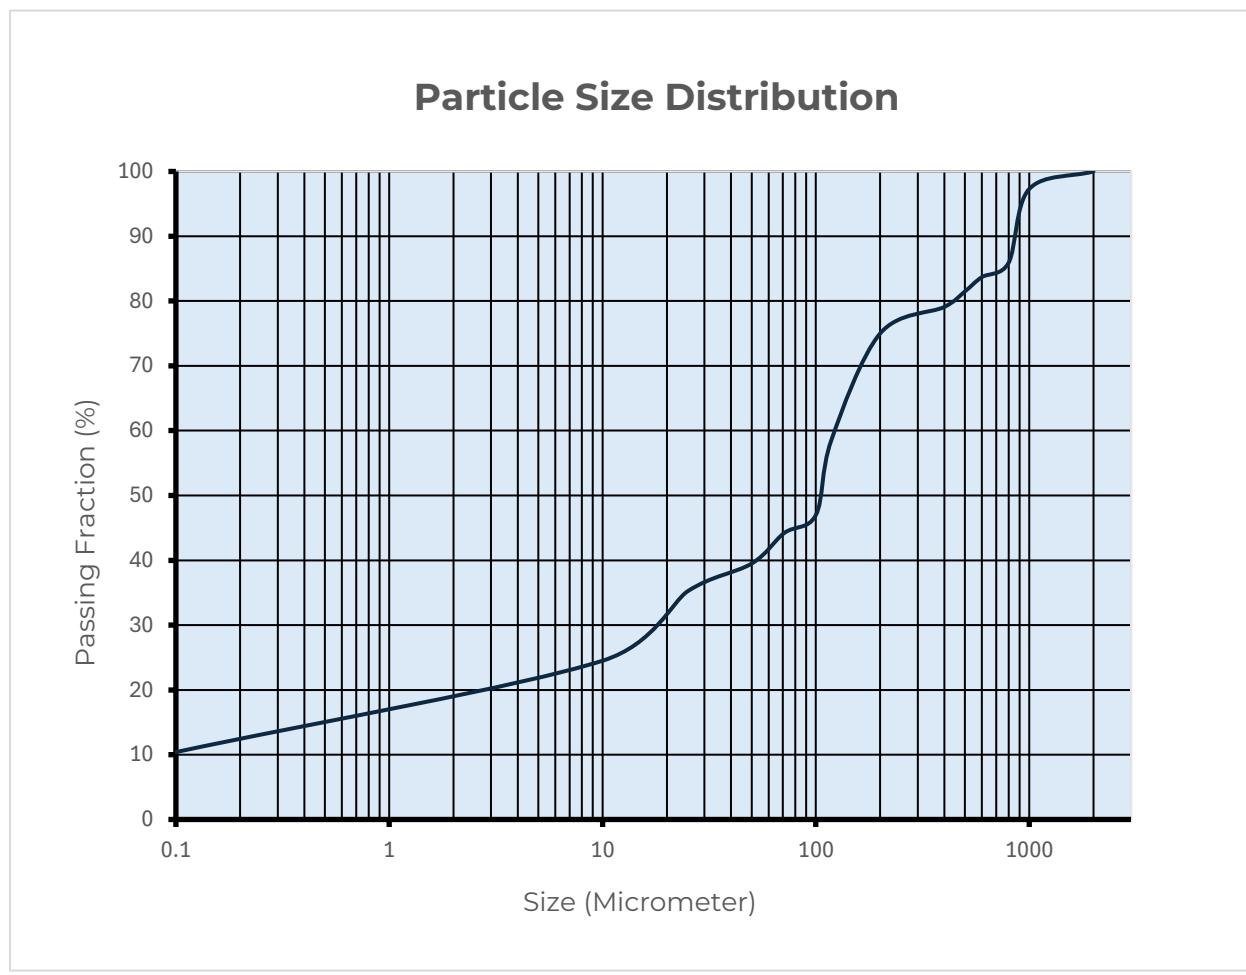

2.5 Particle Geometry

Particle geometry measured through Dynamic Image Analysis performed by a third-party entity with a CAMSIZER X2.

Aspect ratio: 0.70287

Root Form Factor/Circularity: 0.88048

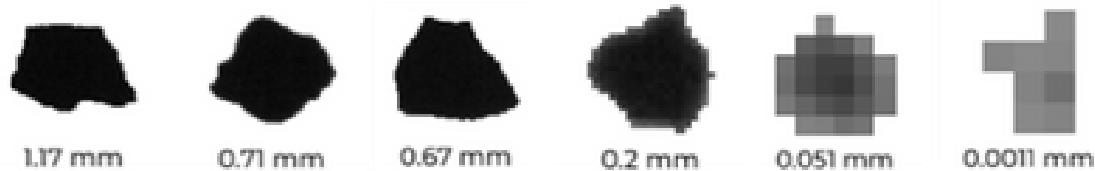


Figure 3: Particle Shape Example at Different Sizes

2.6 Shear Stress - Cohesion (c) and Angle of Internal Friction (ϕ^0)

Cohesion and Internal Angle of Friction measured through Direct shear test Performed at UPM-ETSIME by the Space Mining Group with a Mecánica Científica S.A. - Direct Shear Cut Machine. Measurements were performed at ~25 kPa and ~50 kPa. The range of normal stress applied in the direct shear tests will be expanded by incorporating lower stress levels, allowing a more complete characterization of the simulant's shear behavior across a broader range of loading conditions.

Internal Angle of Friction (ϕ^0): 45.342°

Cohesion (c): 2.369 kPa

2.7 Magnetic Susceptibility

The massive magnetic susceptibility was obtained through a magnetic susceptibility analysis performed by UGR-CIC with a PPMS DynaCool Magnetometer with an ACMS II Module.

$$\chi_m = 4495.7 \times 10^{-9} \text{ m}^3/\text{kg}$$

3. Other Information

- Safety data sheet available on request.
- **Revision date:** December 4th 2025.